

**SYNTHESIS AND PROPERTIES OF PYRAZINO[2,3-*g*]QUINOXALINE
DERIVATIVES: BLUE AND GREEN FLUORESCENT MATERIALS
WITH ELECTRON AFFINITY**

**Katsuhiko Ono,* Yutaka Okazaki, Masakazu Ohkita, Katsuhiro Saito,* and
Yoshiro Yamashita[†]**


Department of Life and Material Engineering, Nagoya Institute of Technology,
Gokiso, Showa, Nagoya 466-8555, Japan; e-mail: k.ono@nitech.ac.jp

[†]Department of Electronic Chemistry, Tokyo Institute of Technology, Nagatsuta,
Midori, Yokohama 226-8502, Japan

Abstract – The title compounds have been synthesized and their optical and electronic properties were surveyed in comparison to those of [1,2,5]thiadiazolo[3,4-*g*]quinoxaline and benzo[1,2-*c*:4,5-*c'*]bis([1,2,5]thiadiazole) derivatives. They are blue or green fluorophores with electron affinity due to the fused pyrazine rings. Substitution of the fused pyrazine ring for the fused 1,2,5-thiadiazole one led to red shifts of *ca.* 50 nm in the fluorescence spectra. The substitution also resulted in an increase of electron affinity in the 14 π -electron systems. Using a series of these compounds, red-green-blue (RGB) fluorescent emission was achieved.

Introduction of fused heterocycles is a useful method for modification of π -conjugation systems together with functional groups. Fused pyrazine and 1,2,5-thiadiazole rings, which are electron-accepting units, have been utilized for organic functional materials.¹ Especially, molecules containing fused thiadiazole rings have been studied as electrical conductors² and magnetic materials.³ Polymers with fused thiadiazole rings were also reported as emission materials in organic electroluminescent (EL) devices.⁴ 4,8-Diphenylbenzo[1,2-*c*:4,5-*c'*]bis([1,2,5]thiadiazole) (**1**), which is a hetero analog of 9,10-diphenylanthracene containing two fused thiadiazole units, showed its absorption maximum at a much longer wavelength and has a high electron affinity comparable to benzoquinone due to the extended 14 π -electron system.⁵ Furthermore, compound (**1**) showed a strong red fluorescence with a long lifetime.⁶ In this context, interest in fused pyrazine rings has been, recently, enlarged in materials science.⁷ Therefore, we

have prepared pyrazino[2,3-*g*]quinoxaline (**2a**) and its 9,10-diaryl derivatives (**2c,d**). Their electronic and optical properties were investigated in comparison to those of compound (**1**) and 4,9-diphenyl[1,2,5]thiadiazolo[3,4-*g*]quinoxaline (**3**) in order to survey the functional effects between fused pyrazine and 1,2,5-thiadiazole rings. We report herein the preparation and properties of **2** and the substitution effect of the fused heterocycles.

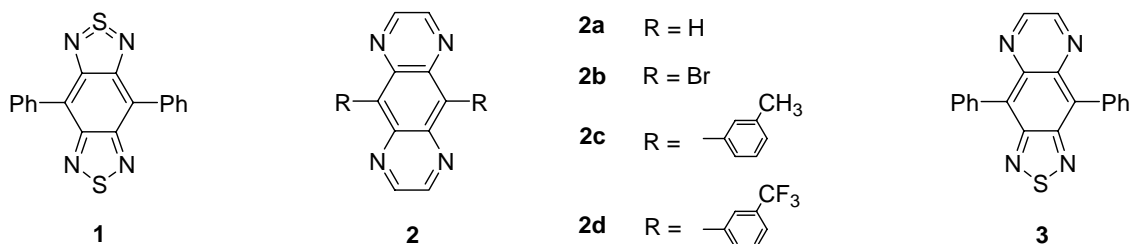

Pyrazino[2,3-*g*]quinoxaline (**2a**) was obtained by oxidation of 1,2,3,4-tetrahydropyrazino[2,3-*g*]quinoxaline with active MnO₂ in refluxing toluene as a modification of the reported method.⁸ Bromination of **2a** with two equimolar amounts of NBS in DMF afforded dibromide (**2b**) in 76% yield. Compounds (**2c**) and (**2d**) were prepared in 60% and 8% yields by the Suzuki coupling reaction of **2b** with the corresponding boronic acids (1 mol % Pd(PPh₃)₄, 1.0 M Na₂CO₃(aq.)/THF, 48 h), respectively. These compounds were isolated as colorless crystals for **2a** (mp 216-218 °C; lit.,⁸ mp 215-216 °C) and yellow crystals for **2b** (mp > 300 °C), **2c** (mp > 300 °C), and **2d** (290 °C decomp). The absorption maxima of **2a,c,d** are listed in Table 1 and are compared with those of compounds (**1**) and (**3**). The maxima of **2c,d** were red-shifted by *ca.* 40 nm from that of **2a** due to the π -conjugation with the aromatic rings at the 9,10-positions. There is no difference between methyl and trifluoromethyl groups as *meta*-functional groups of the aromatic rings. The absorption maxima of **3** and **1** are moved to longer wavelength of *ca.* 80 nm from those of **2c** and **3**, respectively, by substitution of the pyrazine moiety for the 1,2,5-thiadiazole one (**2c**→**3**→**1**). These red shifts are ascribable to a lowering of the LUMO energies in the 14 π -electron systems.

Table 1. Absorption maxima and emission maxima in dichloromethane

Compound	$\lambda_{\text{abs, max}}/\text{nm}$ (log ϵ)	$\lambda_{\text{em, max}}/\text{nm}$
2a	356 (4.08)	466
2c	398 (3.91), 364 (4.04)	509
2d	394 (3.84), 361 (4.01)	493
3 ^a	471 (3.99), 363 (4.26)	561
1 ^a	558 (3.99), 359 (4.33)	624

^aReference 5.

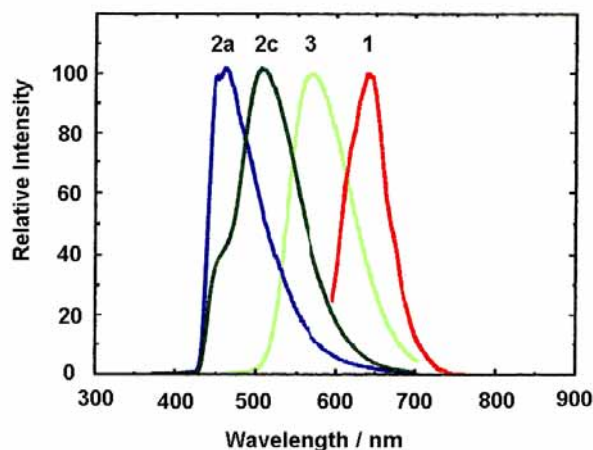


Figure 1. Fluorescence spectra of **1**, **2a**, **2c**, and **3** in CH_2Cl_2 .

Figure 1 shows fluorescence spectra of **2a,c** in dichloromethane together with those of compounds (**1**) and (**3**). Four spectra were observed at the extended wavelength region from 420 to 730 nm (Table 1). The emission maximum of **2c** was observed at the longer wavelength of *ca.* 40 nm than that of **2a**. Furthermore, the emission maxima of **3** and **1** are shifted to longer wavelengths of *ca.* 50 nm from those of **2c** and **3**, respectively, by exchanging the pyrazine ring for the 1,2,5-thiadiazole one (**2c**→**3**→**1**). The fluorescent color is, depending on the shift of the spectra, blue for **2a**, blue green for **2d**, green for **2c**, yellow green for **3**, and red for **1**. This result indicates that the fluorescent properties are determined by fused heterocycles; pyrazine and 1,2,5-thiadiazole. In addition, RGB fluorescent emission was achieved by a set of these compounds (**1**, **2c**, and **2a**).

The cyclic voltammograms (CV) of **2a,c,d** in dichloromethane showed two reversible one-electron redox waves. The half-wave reduction potentials are given in Table 2. Since the reduction potentials of **2c,d** are similar to that of **2a**, the aromatic rings have little influence on the electron affinity of the 14π -electron systems. The electron affinity increases by exchanging the pyrazine ring for the 1,2,5-thiadiazole one (**2**→**3**→**1**). Their electron-accepting properties are also determined by selection of the fused heterocycles.

Table 2. Half-wave reduction potentials in the cyclic voltammetry^a

Compound	$E_1^{\text{red}}/\text{V}$	$E_2^{\text{red}}/\text{V}$	$\Delta E/\text{V}$
2a	-0.95	-1.48	0.52
2c	-0.97	-1.48	0.50
2d	-0.91	-1.48	0.57
3 ^b	-0.82	-1.46 ^c	0.64
1 ^b	-0.61	-1.30	0.69

^a0.1 M *n*-Bu₄NClO₄ in CH_2Cl_2 , Pt electrode, scan rate 100 mV s⁻¹, V vs SCE.

^bReference 5. ^c $E_{\text{pc}} + 0.03$ V.

In summary, we have prepared pyrazino[2,3-*g*]quinoxaline derivatives (**2**), which are blue or green fluorophores with electron affinity. Their optical and electronic properties were discussed together with those of compounds (**1**) and (**3**). The fluorescent color and electron affinity can be controlled by selection of the fused heterocycles; pyrazine and 1,2,5-thiadiazole. RGB fluorescent emission was achieved by a series of the fluorophores with high electron affinity.

ACKNOWLEDGEMENTS

This work was supported by the Yazaki Memorial Foundation for Science and Technology.

REFERENCES

1. a) T. Yamamoto, K. Sugiyama, T. Kushida, T. Inoue, and T. Kanbara, *J. Am. Chem. Soc.*, 1996, **118**, 3930; b) C. Kitamura, S. Tanaka, and Y. Yamashita, *Chem. Mater.*, 1996, **8**, 570; c) Y. Yamashita, S. Tanaka, K. Imaeda, H. Inokuchi, and M. Sano, *J. Chem. Soc., Chem. Commun.*, 1991, 1132; d) S. Mataga, H. Goromaru, T. Thies, M. Kadowaki, and S. Maeda, Jpn Patent 2003104976 (*Chem. Abstr.*, 2003, **138**, 295026e); e) T. Suzuki, T. Fukushima, Y. Yamashita, and T. Miyashi, *J. Am. Chem. Soc.*, 1994, **116**, 2793; f) M. Karikomi, C. Kitamura, S. Tanaka, and Y. Yamashita, *J. Am. Chem. Soc.*, 1995, **117**, 6791; g) K. Ono, A. Adachi, K. Okita, M. Goto, and Y. Yamashita, *Chem. Lett.*, 1998, 545.
2. a) T. Naito, H. Kobayashi, A. Kobayashi, and A. E. Underhill, *Chem. Commun.*, 1996, 521; b) Y. Yamashita, M. Tomura, and K. Imaeda, *Chem. Commun.*, 1996, 2021; c) Y. Yamashita, K. Ono, M. Tomura, and K. Imaeda, *Chem. Commun.*, 1997, 1851; d) K. Ono, S. Tanaka, K. Imaeda, and Y. Yamashita, *J. Chem. Soc., Chem. Commun.*, 1994, 899.
3. a) M. Fujimori, Y. Suzuki, H. Yoshikawa, and K. Awaga, *Angew. Chem., Int. Ed.*, 2003, **42**, 5863; b) P. A. Stuzhin, E. M. Bauer, and C. Ercolani, *Inorg. Chem.*, 1998, **37**, 1533; c) E. M. Bauer, D. Cardarilli, C. Ercolani, P. A. Stuzhin, and U. Russo, *Inorg. Chem.*, 1999, **38**, 6114.
4. a) I. S. Millard, *Synth. Met.*, 2000, **111-112**, 119; b) Y.-H. Niu, J. Huang, and Y. Cao, *Adv. Mater.*, 2003, **15**, 807.
5. a) K. Ono, S. Tanaka, and Y. Yamashita, *Angew. Chem., Int. Ed. Engl.*, 1994, **33**, 1977; b) Y. Yamashita, K. Ono, M. Tomura, and S. Tanaka, *Tetrahedron*, 1997, **53**, 10169.
6. M. Kono, *Chem. Phys.*, 2002, **282**, 101.
7. a) J. Nishida, Naraso, S. Murai, E. Fujiwara, H. Tada, M. Tomura, and Y. Yamashita, *Org. Lett.*, 2004, **6**, 2007; b) T. Kobayashi and S. Kobayashi, *Eur. J. Org. Chem.*, 2002, 2066.
8. J. Harley-Mason and A. H. Laird, *Tetrahedron*, 1959, **7**, 70.